

# Horseradish peroxidase catalyzed free radical cannot free move in reaction solution

Cai Xialing\*, Ma Lin

Received: 4 March 2009 / Received in revised form: 4 March 2009, Accepted: 17 March 2009, Published online: 16 September 2009  
© Sevas Educational Society 2008

## Abstract

Mechanism of Horseradish Peroxidase -catalyzed phenol compound oxidizing reaction is a radical polymerization. Many polymer preparation are also carry on through the radical polymerization mechanism. We deduce if free radical produced by peroxidase-catalyzed phenol polymerization could apply on polymer preparation? Could the phenol-oxygen free radical leave off the peroxidase and catalyze other compounds polymerization? The free radical in phenol oxidation process was investigated in homogeneous reaction and in immobilized HRP catalyzed reaction. The results showed the free radical produced by peroxidase only move on the surface of enzyme, can't free move in solution in both experiment. Evidence showed the phenol polymerization is enzyme reaction process, different from general chemistry free radical chain reaction.

**Keywords:** Horseradish Peroxidase, free radical polymerization, mechanism

## Introduction

Peroxidase widely exists in the higher plant, richest in the fig sap and the horse radish. horseradish peroxidase [HRP, E.C.1.11.1.7] separated from the horse radish is the most commonly used peroxidase. HRP, molecular weight 40000, isoelectric point 7.2, most suitable pH (in aqueous phase) 7.0, and take the hard heme as the prosthetic groups. In the catalyzed process, HRP responded with the hydrogen peroxide specificity, phenols compound and aromatic amines as hydrogen donor, the enzyme-oxygen free radical formed after providing H, then rearranging and coupling to form Oligomers (Gajhede *et al* 1997; Hernandez-Ruiz *et al* 2001; Keilin *et al* 1951; Meunier *et al* 1998; Nakajima *et al* 1987).

---

Cai Xialing\*, Ma Lin

School of Chemistry and Chemical Engineering, Sun Yat-Sen University, Guangzhou, People's Republic of China

\*Tel: 0086 20 84113356

Fax: 0086 20 84113690

E-mail: cesx1@mail.sysu.edu.cn

Horseradish peroxidase catalysis's phenol compound oxidizing reaction is one kind of radical polymerization response (Araiso *et al* 1976; Gunilla *et al* 2005; Harris *et al* 1993; Jones 2001; Keilin *et al* 1955). Many polymer preparation are also carry on through the radical polymerization reaction. So we once attempted copolymerization of phenol and styrene, acrylic amide, methyl methacrylate to synthesis functional polymer by peroxidase catalyzed, initiated by H<sub>2</sub>O<sub>2</sub>. Although experiments repeatedly, the free radical produced by peroxidase catalysis hydrogen peroxide cannot initiate styrene, acrylamide, methyl methacrylate polymerization, and reaction that peroxidase catalyzes the phenol compound (p-Phenylphenol, p-Methyphenol) with styrene, acrylamide, methyl methylacrylate copolymerization also cannot carry on. So hypothesized the free radical can't free move produced by peroxidase catalysis hydrogen peroxide, two experiments were designed to prove the idea.

## Experimental

### Material and Characterization

Horseradish peroxidase (HRP E.C.1.11.1.7), 225 units/mg (25 °C, guaiacol, H<sub>2</sub>O<sub>2</sub>) was obtained from Roche (Mannheim, Germany). ESR spectra were measured on Bruker ESR 200D, 9.8 GHz, 100 KHz, ESR Spectra of free radical caught by DMPO (5.5-dimethyl-1-proline N-Oxied).

### Preparation of HRP immobilization

After washing with NaOH, the self-made agar-agar bead were resuspended in 12 ml acetone, add Cyanuric chloride dissolved with dioxane and acetone. The reaction mixture was stirred for 3 min. Then, add 20% acetic acid (v/v) to stop the reaction. Wash with acetone and water separately. Add HRP to the activated agar-agar bead for reaction 3 hour. Immobilized HRP was obtained after wash the carrier with water to eliminate the residuary enzyme. The activity of immobilized HRP is 67.8U/mg, the coupling rate is 86.87%, the coupling quantity is the 7.819mgPr/g agar-agar, enzyme vigor recycling is 24%, enzyme recovery is 24%. (Akkara *et al* 1991; Kumar *et al* 2005; Livage *et al* 2001; Wilson *et al* 1986)

### HRP activity

A mixture of 0.23ml phosphoric acid buffer (pH6.0,10mmol/L), 0.1 ml hydrogen peroxide solution( $0.147\text{mol}\cdot\text{l}^{-1}$ ), 0.32ml trihydroxybenzene solution (5%,v/v), 2.1ml distilled water were stirred in quartz cell at 20 . Air or the distilled water as the blank control, add 0.1ml HRP, blending, measure  $A_{420\text{nm}}$  increasing rate (Bergmeyer 1975).

### Free Radical Detection in Homogeneous Reaction

Add HRP in dialysis bag (blocking molecular weigh 15000D).Put dialysis bag in a 250 ml beaker. Then pour substrate (p-Phenylphenol, sigma) and  $\text{H}_2\text{O}_2$  into solution outside dialysis bag dissolved in 70 % Dioxane/Water (v/v). Detect ESR spectra of free radical in or out dialysis bag (Fig 1.1).

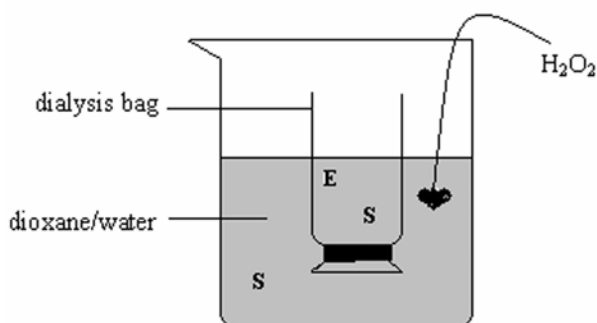


Fig 1.1 Scheme of enzymatic polymerization of p-phenylphenol in a dialysis bag. The reaction medium is the mixture of 70% dioxane and 30% water mixture containing  $0.05\text{mol}\cdot\text{l}^{-1}$  p-phenylphenol. The reaction was initiated by the addition of  $1\mu\text{l}$ ,  $0.1\text{mol}\cdot\text{l}^{-1}$   $\text{H}_2\text{O}_2$  to the outside of the dialysis bag.

### Free Radical Detection in Immobilized HRP catalyzed Reaction

In reaction mixtures, add certain solubility substrate (p-Phenylphenol, sigma) and the immobilized HRP in 70%Dioxane/Water (v/v),  $\text{H}_2\text{O}_2$  added later. Put the immobilized HRP in the capillary vessel base, detect the ESR spectra of free radical when the capillary vessel to be in or to be out from the resonant cavity (Fig 2.1).

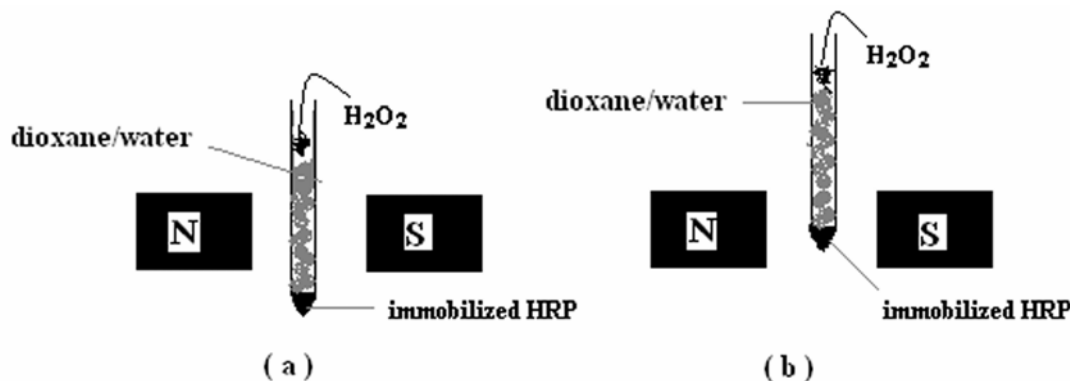


Fig 2.1 Scheme of measurements of ESR spectra with the immobilized enzyme: (a) in and (b) out the magnetic fields

## Results and Discussion

### Free Radical Detection in Homogeneous Reaction

In order to examine free radical which produced by peroxidase-catalyzed hydrogen peroxide can free move or not in the reaction, we add HRP to the dialysis bag (blocking molecular weight 15000D). Put substrate and  $\text{H}_2\text{O}_2$  outside the dialysis bag. HRP(MW40000D) can't permeate the bag, and substrate p-Phenylphenol (MW170D) can free move in or out dialysis bag. Precipitation was observed in the bag to approve the substrate move into the bag interior. Reacting 3 hour later, solution outside dialysis bag was taken out to detect. No polymer has been discovered by HPLC analysis. At the same time, we also tested by the paramagnetic, discovered that the dialysis bag interior solution had the free radical signal, but the exterior solution did not have. (Fig 1.2)

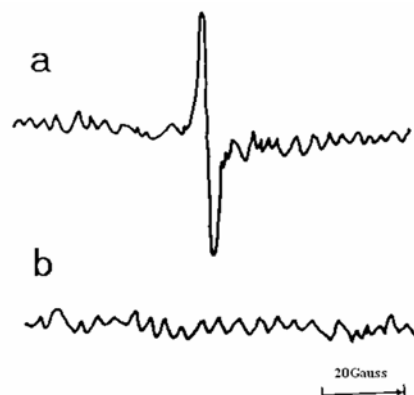


Fig 1.2 The ESR spectrum of the solution: (a) inside and (b) outside the dialysis bag.

By HPLC and ESR, we thought that the free radical polymerization is limited in dialysis bag interior, does not enter outside in the dialysis bag's solution in the reaction process. So deduce that life of phenol oxygen free radical and phenols' free radical are short, phenol oxygen free radical's formation as well as later rearrangement, coupling, polymerization carry on nearby the

enzyme active centers in the reaction process. The enzyme not only produces free radical in the response, but also provide a field for the free radical, namely a sparse water region lies nearby the enzyme active centers, reaction occur at here. To further confirm the supposition, we utilize paramagnetic technical and immobilized enzyme technology to analysis the response.

#### Free Radical Detection in Immobilized HRP catalyzed Reaction

HRP immobilized in agar-agar bead put in the capillary vessel base in the paramagnetic meter sample area. Adjust capillary vessel altitude to enable immobilized HRP to be in or out the resonant cavity. In the same experiment condition, ESR spectra were detected in Fig 2.2. Fig 2.2 showed the free radical signal did not examine when the enzyme emigrates outside the resonant cavity. This system does not have any shielding device, therefore it powerfully proved our deduction accuracy.

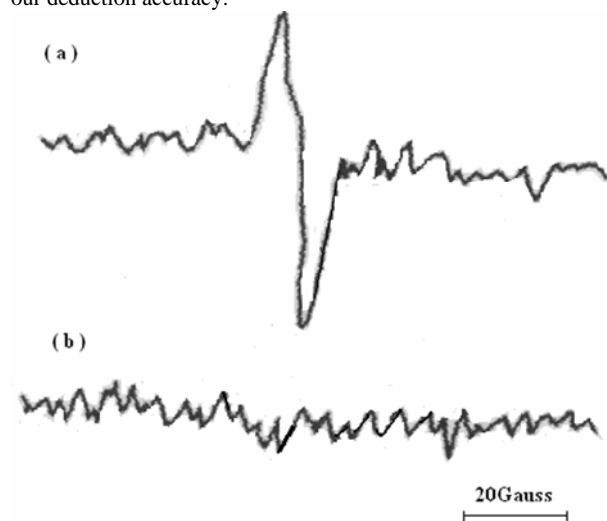


Fig 2.2 The ESR spectra of the solution with the immobilized enzyme (a) in and (b) out the magnetic field.

In Immobilized Enzyme Catalyze phenylphenol polyreaction, we discovered that when add immobilized HRP in reaction solution, the precipitation did not present in the solution, but only observed that the colorless agar-agar bead turned into black (Fig 3). This

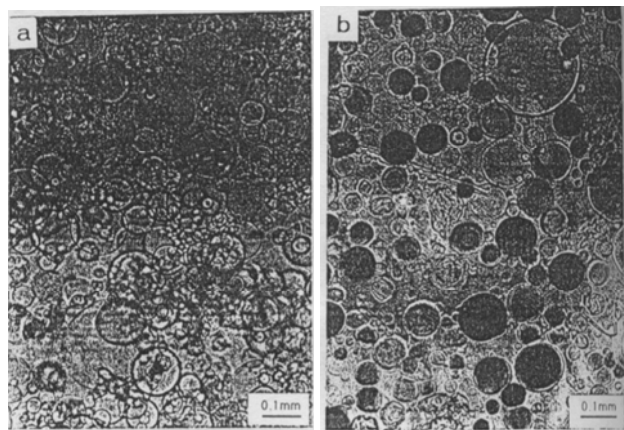


Fig.3. The microphotographs of the reaction catalyzed by immobilized enzymes. The reaction was performed on carrier plate. One drop of reaction solution was put on, which contained immobilized HRP and  $0.01 \text{ mol.l}^{-1}$  p-phenylphenol. The photograph (a) and (b) were taken before and after the addition of  $1 \mu\text{l}$ ,  $0.1 \text{ mol.l}^{-1}$   $\text{H}_2\text{O}_2$  for 10 minutes, respectively.

phenomenon showed the free radical produced by the enzyme catalyze has not diffused into the solution, only happened on enzyme surface, so the product formed adhered to surface of the immobilized HRP (agar-agar bead). The above result may explain that peroxidase catalyzed the phenol polyreaction is different with the general sense chemistry free radical chain reaction. Here, peroxidase participate in each reaction step, the entire reaction is an enzyme catalysis process.

Although the peroxidase catalyzing hydrogen peroxide or the phenol oxygen free radical cannot free move in the solution, Horseradish peroxidase-mediated polymerization of styrene and methyl methacrylate were succeeded when beta-diketones as initiator in recent years (Kalra *et al* 2000; Singh *et al* 2000). In the reaction process, stoichiometric ratio of hydrogen peroxide and styrene or methyl methacrylate is not equal, the free radical produced by enzyme-catalyzed hydrogen peroxide captured by beta-diketones, subsequently initiated methyl methacrylate or the styrene polymerization. Therefore this kind of polymerization is completely different from peroxidase catalysis phenol compound's polymerization (Silvia *et al* 2008; Wei *et al* 2002).

#### Conclusions

We investigated the free radical in phenol oxidation process in two designed experiments: a homogeneous reaction and a immobilized HRP catalyzed reaction. The results showed the free radical produced by peroxidase only move on the surface of enzyme, can't free move in solution in both experiment. The phenol polymerization is enzyme reaction process, different from general chemistry free radical chain reaction.

#### Acknowledgements

This work was supported by Sun Yat-Sen University Research Fund.

#### References

- Araiso T, Miyoshi K, Yamazaki I (1976) Mechanisms of electron transfer from sulfite to horseradish peroxidase-hydroperoxide compounds. *Biochemistry* 15:3059-3063
- Gajhede M, Schuller DJ *et al* (1997) Crystal structure of horseradish peroxidase C at 2.15 Å resolution. *Nat Struct Biol* 4:1032-1038
- Gunilla H Carlsson, Peter Nicholls *et al* (2005) Complexes of Horseradish Peroxidase with Formate, Acetate, and Carbon Monoxide. *Biochemistry* 44(2):635-642
- Harris RZ, Newmyer SL, Ortiz De Montellano PR (1993) Horseradish peroxidase-catalyzed two-electron oxidations: Oxidation of iodide, thioanisoles, and phenols at distinct sites. *J Biol Chem* 268:1637-1645
- Hernandez-Ruiz J, Arnao MB *et al* (2001) Catalase-like activity of horseradish peroxidase: relationship to enzyme inactivation by  $\text{H}_2\text{O}_2$ . *Biochem J*, 354:107-114
- Bergmeyer HU (1974) *Methods of enzymatic analysis*, Verlag Chemie; Academic Press, New York, Weinheim, New York
- Akkara JA, Senecal KJ, Kaplan DLJ (1991) Synthesis and characterization of polymers produced by horseradish peroxidase in dioxane. *J Polym Sci Polym Chem* 29:1561-1574
- Livage J, Coradin T, Roux C (2001) Encapsulation of biomolecules in silica gels. *J Phys-Condens Mat* 13:R673-R691
- Jones P (2001) Roles of water in heme peroxidase and catalase mechanisms. *J Biol Chem*, 276:13791-13796

- Keilin D, Hartree EF (1951) Purification of horseradish peroxidase and comparison of its properties with those of catalase and methaemoglobin. *Biochem J* 49:88-104
- Keilin D, Hartree EF, Catalase (1955) peroxidase and metmyoglobin as catalysts of coupled peroxidatic reactions. *Biochem J* 60:310-325
- Kalra B, Gross RA (2000) Horseradish peroxidase mediated free radical polymerization of methyl methacrylate. *Biomacromolecules* 1(3):501-505
- Meunier B, Rodriguez-Lopez JN et al (1998) Redox- and anion-linked protonation sites in horseradish peroxidase: Analysis of distal haem pocket mutants. *Biochem J* 330:303-309.
- Nakajima R, Yamazaki I (1987) The mechanism of oxyperoxidase formation from ferryl peroxidase and hydrogen peroxide. *J Biol Chem* 262: 2576-2581
- Wilson RJH, Kay G, Lilly MD (1968) The preparation and kinetics of lactate dehydrogenase attached to water-insoluble particles and sheets. *Biochem J* 108: 845-853
- Kumar R, Maitra AN et al (2005) Hollow gold nanoparticles encapsulating horseradish peroxidase. *Biomaterials* 26:6743-6753
- Silvia Villarroya, Kristofer J Thurecht, Steven M (2008) Howdle HRP-mediated inverse emulsion polymerisation of acrylamide in supercritical carbon dioxide. *Green Chem* 10:863-867
- Singh A, Ma D, Kaplan DL (2000) Enzyme-mediated free radical polymerization of styrene. *Biomacromolecules* 1(4):592-596
- Wei Guo, and Patricia Ann Mabrouk (2002) Raman Evidence that the Lyoprotectant Poly(ethylene glycol) Does Not Restore Nativity to the Heme Active Site of Horseradish Peroxidase Suspended in Organic Solvents. *Biomacromolecules* 3 (4):846-849